

Pressure-decoupled magnetic and structural transitions of the parent compound of iron-based 122 superconductors BaFe_2As_2

J. J. Wu^{a,b}, Jung-Fu Lin^{b,1}, X. C. Wang^a, Q. Q. Liu^a, J. L. Zhu^a, Y. M. Xiao^c, P. Chow^c, and Changqing Jin^{a,1}

^aInstitute of Physics, Chinese Academy of Sciences, Beijing 100190, China; ^bDepartment of Geological Sciences, Jackson School of Geosciences, The University of Texas at Austin, Austin, TX 78712; and ^cHigh Pressure Collaborative Access Team, Carnegie Institution of Washington, Advanced Photon Source, Argonne National Laboratory, Argonne, IL 60439

Edited[†] by Ho-kwang Mao, Carnegie Institution of Washington, Washington, DC, and approved September 3, 2013 (received for review May 30, 2013)

The recent discovery of iron ferropnictide superconductors has received intensive concern in connection with magnetically involved superconductors. Prominent features of ferropnictide superconductors are becoming apparent: the parent compounds exhibit an antiferromagnetic ordered spin density wave (SDW) state, the magnetic-phase transition is always accompanied by a crystal structural transition, and superconductivity can be induced by suppressing the SDW phase via either chemical doping or applied external pressure to the parent state. These features generated considerable interest in the interplay between magnetism and structure in chemically doped samples, showing crystal structure transitions always precede or coincide with magnetic transition. Pressure-tuned transition, on the other hand, would be more straightforward to superconducting mechanism studies because there are no disorder effects caused by chemical doping; however, remarkably little is known about the interplay in the parent compounds under controlled pressure due to the experimental challenge of in situ measuring both of magnetic and crystal structure evolution at high pressure and low temperatures. Here we show from combined synchrotron Mössbauer and X-ray diffraction at high pressures that the magnetic ordering surprisingly precedes the structural transition at high pressures in the parent compound BaFe_2As_2 , in sharp contrast to the chemical-doping case. The results can be well understood in terms of the spin fluctuations in the emerging nematic phase before the long-range magnetic order that sheds light on understanding how the parent compound evolves from a SDW state to a superconducting phase, a key scientific inquiry of iron-based superconductors.

ferropnictide-type superconductor | high-pressure effect | spin order

High pressure is very effective to modify crystal or electronic structures that often lead to new material states of interdisciplinary interest from geosciences across chemistry to physics (1–5). Pressure is especially unique in generating or tuning superconducting states with the advantage of not introducing disorder effects in comparison to chemical doping (3); hence it is more favorable to intrinsic properties studies. The recent discovery of iron pnictide (or ferropnictides) superconductors (6–9) has shed new light on unconventional superconductors involved with magnetic elements that are previously considered to be incompatible to superconductivity. The spins of iron in ferropnictides are periodically modulated and localized in space forming the spin density wave (SDW) parent state, whereas such antiferromagnetically ordered magnetism (AFM) is also closely related to the superconductivity in cuprates and other unconventional superconductors. Magnetism has been suggested to play a crucial role in the occurrence of high T_C in ferropnictides, in which the paramagnetic (PM) to AFM transition is accompanied by a tetragonal-to-orthorhombic structural transition in systems like LaFeAsO (10) or BaFe_2As_2 (11).

The 122 ternary AFe_2As_2 (A = alkaline metals Ca, Sr and Ba) compounds, characterized by pairs of tetrahedral FeAs layers, have clearly demonstrated pressure-induced high T_C superconductivity

with well-defined magnetic and structural characteristics (12–15). Upon cooling, the undoped parent compounds of the 122 system exhibit a tetragonal-to-orthorhombic structural transition strongly coupled by a paramagnetic-to-antiferromagnetic transition that takes place at the temperature that coincides with the structural-phase transition (14). Chemical doping has been found to strongly suppress this transition. Recent study on $\text{Ba}(\text{Fe}_{1-x}\text{Co}_x)_2\text{As}_2$ shows that the structural transition precedes the magnetic transition in decreasing temperature for a fixed amount of chemical-doping fraction (16). Moreover, experimental results on underdoped $\text{Ba}_{0.84}\text{K}_{0.16}\text{Fe}_2\text{As}_2$ single crystals, with excellent chemical homogeneity, have further shown that the magnetic and structural transitions are indeed separated (17) with the structural transition occurring at higher temperature. It is noted that the antiferromagnetic transition is always preceded by or coincident with a tetragonal-to-orthorhombic structural distortion. This observation indicates that the structural distortion is related to an electronic-phase transition due to C4 symmetry break as a result of long-range ordering (18–20).

High pressure has been shown to effectively suppress AFM ordering and to induce a high T_C in the system (21, 22). Similar to the chemical doping, applied pressure has been found to cause the same effects on tuning the SDW state to superconductivity (23–28). Because AFM ordering is strongly coupled with structural distortion, further investigation under controlled pressure temperature (P - T) conditions using in situ probes sensitive to these transitions is needed to unravel the intrinsic interplay between structure and magnetism in the parent compound of iron-based superconductors. Here we report the studies on the

Significance

Superconductivity and magnetism have been considered to be in competition with each other. The discovery of high- T_C superconductivity in iron-based compounds, however, drastically alters this concept, as the origin of its superconductivity is closely related to magnetism of iron. Here we report the interplay of magnetic and structural transitions in a parent compound of iron-based superconductor BaFe_2As_2 at high pressures, in which magnetic ordering precedes the structural transition at high pressures. Our results can be understood in terms of spin fluctuations in the emerging nematic phase before long-range magnetic order. Our findings provide valuable insights into exploring the interplay between magnetism and structure hence to better understand the superconductivity in iron-based compounds.

Author contributions: J.-F.L. and C.J. designed research; J.J.W., Q.Q.L., and J.L.Z. performed research; X.C.W., Y.M.X., and P.C. contributed new reagents/analytic tools; J.J.W., J.-F.L., and C.J. analyzed data; and J.J.W., J.-F.L., and C.J. wrote the paper.

The authors declare no conflict of interest.

[†]This Direct Submission article had a prearranged editor.

Freely available online through the PNAS open access option.

¹To whom correspondence may be addressed. E-mail: jin@iphy.ac.cn or afu@jsg.utexas.edu.

magnetic and structural transitions of BaFe_2As_2 investigated using synchrotron Mössbauer spectroscopy (SMS) and X-ray diffraction (XRD) in a cryogenically cooled high-pressure diamond anvil cell (DAC) with a highly hydrostatic pressure medium of neon. Study of the 122 system at high pressures was chosen as high-quality single-crystal and powder samples can be well synthesized and prepared. Our SMS spectra with very high energy resolution were used to derive hyperfine parameters that are extremely sensitive to the local magnetic moment ordering of the sample, whereas microfocused XRD patterns provide information on lattice parameters and their degrees of distortion. The combined results show that mesoscopic magnetic ordering that can be detected by subtle SMS precedes the structural distortion over temperature cooling at high pressures, different from that of chemical doping where the crystal structure transitions always precede the magnetic-phase transitions. These results indicated the emerging nematic phase before long-range spin order.

Results and Discussion

The temperature-dependent SMS spectra for BaFe_2As_2 at various pressures are well represented by the modeled SMS spectra (Fig. 1). The higher-temperature tetragonal-phase exhibits paramagnetism such that its SMS spectrum is shown as a smooth, exponentially decayed line (29). Over temperature decrease at high pressures, BaFe_2As_2 undergoes a magnetic transition with the occurrence of the hyperfine magnetic moments shown as the first minimum quantum beat in the SMS spectra (Fig. 1). Our derived hyperfine magnetic field is consistent with previous results under ambient pressure and low temperatures (30); at 100 K and ambient pressure, our calculated hyperfine field is 5.1 (± 1.0) T compared with 5.23 T observed at 77 K in the literature (30). The derived hyperfine magnetic fields as a function of temperature show the onset of the magnetic transition with a sharp increase in the magnetic moment (Fig. 2). As pressure increases, the hyperfine magnetic field decreases, and the magnetic transition region broadens, implying the suppressed magnetism by applied pressure. The magnetic transition pressure in the powder sample is slightly lower than that in the single-crystal sample at a given temperature, indicating that enhanced anisotropic strain decreases the magnetic transition pressure.

Rietveld full-profile refinements of the microfocused XRD spectra show the tetragonal (space group: $I4/mmm$) to orthorhombic

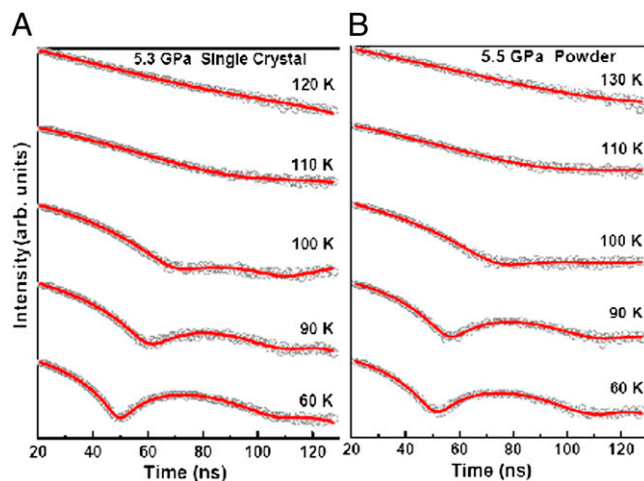


Fig. 1. Representative temperature-dependent SMS spectra of BaFe_2As_2 in Ne pressure medium. (A) Single crystal at 5.3 GPa. (B) Powder sample at 5.5 GPa. \circ , experimental data; red solid lines, modeled spectra using the CONUSS program. Quantum beats in the spectra represent the occurrence of the magnetic fields and hence the AFM state, whereas the absence of beats (flat spectral feature) indicates the PM state.

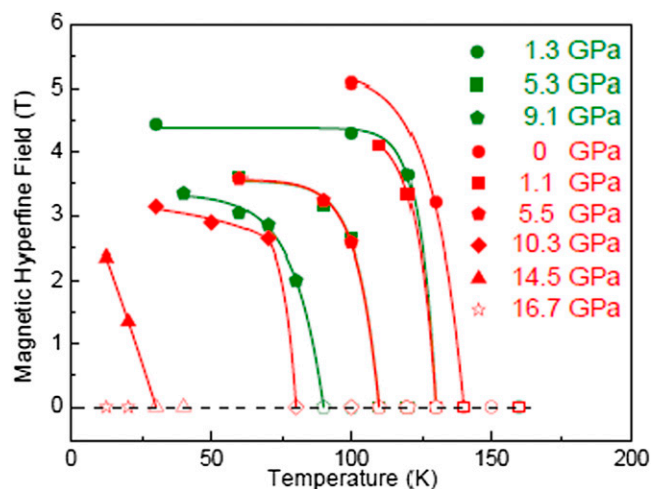


Fig. 2. Derived hyperfine magnetic fields of BaFe_2As_2 as a function of temperature at high pressures. Red symbols, powder in Ne medium; olive symbols, single crystal in Ne medium; solid symbols, AFM state; open symbols, PM state; solid lines, simple fitting to the data.

(space group: $Fmmm$) structural transition with decreasing temperature at 12.5 GPa (Fig. 3A). The (220) line can be well modeled for a single peak at 80 K in the tetragonal phase, whereas it is evident that the (220) line splits into (400) and (040) peaks at 15 K. The variation of the lattice parameters with decreasing temperature is depicted in Fig. 3B. As the splitting of the (220) peak in the tetragonal structure to the (400) and (040) peaks in the orthorhombic structure at 30 K, the a axis splits into a and b axes, showing the onset of the structural transition in the P - T phase diagram (Figs. 3 and 4). We also show a portion of the diffraction patterns of BaFe_2As_2 at selected pressures at 15 K with 2θ between 14.3° and 20° in Fig. 3C. The (400) and (040) peaks merged into a single peak at around 13.7 GPa, indicating that applied pressure drives the structural transition from the tetragonal to the orthorhombic phase at 15 K.

Using both high-resolution SMS and XRD results, we have constructed the phase diagram of BaFe_2As_2 as a function of high pressures and low temperatures (Fig. 4). The extreme energy sensitivity plus high spatial resolution based on synchrotron Mössbauer effects at high pressure provide the possibility to detect mesoscopic ordered local magnetic moment, i.e., the nematic phase which will be addressed in greater detail in the text. Thus, obtained magnetic-order temperature is assigned to T^* as shown in Fig. 4, whereas the structural transition temperature (T_S) was derived from the refined XRD patterns. Because the magnetic transition occurs over a certain temperature region at a given pressure, the onset of the T^* is derived as the mean of the two experimental temperatures between the last appearance of the PM state and the first appearance of the AFM state (Figs. 2 and 4). For comparison, the superconducting temperature (T_C) was taken from previous electrical resistivity measurements using hydrostatic medium similar to our experiments (28). Below 3 GPa, the magnetic transition occurs over a narrower temperature region, and the T^* curve coincides with the T_S by XRD and resistivity measurements as shown in Figs. 2 and 4. At higher pressures, the magnetic transition broadens, and the onset of the T^* curve increasingly precedes the T_S curve in temperature decrease even up to about 15 GPa, where the magnetic ordering has been completely suppressed.

The separation and deviation of the structural and magnetic transitions has been reported in 1111-type LaFeAsO and NdFeAsO , with the structural transition preceding the magnetic transition (31, 32). However, in the peculiar 122-type parent

and interaction of the electron spins thus play a key role in the origin of superconductivity in pnictides. These results enable one to understand how the magnetic order in a mesoscopic scale proceeds to the macroscopic crystal structure-phase transition in high- T_C ferropnictide. These high-pressure results reveal a pure tuning on the physics of the system that is distinct from the chemical doping, providing valuable, direct insight into exploring the interplay between magnetism and structure transitions.

Methods

Single-Crystal Growth. Single-crystalline BaFe_2As_2 samples with 20 atom% ^{57}Fe enrichment were grown by the FeAs self-flux method (15).

Magnetic Moment Detection at High Pressures. Powder samples were gently ground from the ^{57}Fe -enriched single crystals and were later used for SMS and X-ray diffraction experiments. SMS experiments were conducted in a membrane DAC at the beamline 16-IDD of the Advanced Photon Source (APS). A synchrotron X-ray beam of $30\text{ (V)} \times 50\text{ (H)} \mu\text{m}$, $\Delta E/E \sim 1 \times 10^{-7}$ in resolution and 14.4125 keV corresponding to the nuclear transition energy of the ^{57}Fe nuclei was used to measure the SMS spectra of ^{57}Fe -doped sample. Both powder and single-crystal samples with $100 \mu\text{m}$ in diameter and $15\text{--}20 \mu\text{m}$ in thickness (corresponding to an effective thickness of five) were used for the experiments to understand the effect of anisotropic stress on the magnetic transition. A rhenium gasket was preindented to a thickness of $30 \mu\text{m}$ by a pair of $400\text{-}\mu\text{m}$ culets, and a hole of $150 \mu\text{m}$ was subsequently drilled in it and used as the sample chamber. The sample was loaded into the sample chamber using Ne as the pressure medium, together with a few ruby spheres for pressure determination. A helium-cooled cold-finger cryostat was used to cool the sample in the DAC to as low as 6 K; temperatures of the DAC were equilibrated for a couple of hours after each cooling and were measured using two thermocouples attached each side of the DAC. Pressures of the sample chamber were controlled by a membrane diaphragm and measured in situ using an online ruby system before and after the SMS collection. To determine the effects of hydrostaticity on the magnetism of the sample, the SMS experiments were also conducted using mineral oil (a mixture of heavy hydrocarbons) as a pressure medium. SMS

spectra were collected by an avalanche photodiode detector at the nuclear forward scattering geometry with a collection time of 1–2 h. The SMS spectra were fitted using the CONUSS (COherent Nuclear resonant Scattering by Single crystals) program (38) to derive the hyperfine magnetic fields.

Structure Characterizations at High Pressures. Angle-dispersive powder XRD measurements were carried out at the 16-IDD beam line of the APS. A monochromatic X-ray beam with a wavelength of 0.37379 \AA and a focused beam size of $5\text{ (V)} \times 10\text{ (H)} \mu\text{m}$ was used. The ^{57}Fe -enriched powder samples were loaded into the same DAC in the same cryostat using a Ne pressure medium and ruby pressure calibrate. Analyses of the XRD patterns, before and after the grinding, showed consistent sample lattice parameters, ensuring that grinding does not introduce additional strain on the sample. The powder XRD measurements were performed at pressure up to 15 GPa from room temperature to 15 K with a typical temperature interval of 10 K. Rietveld full-profile refinements of the XRD pattern were performed using the GSAS (General Structural Analysis System) package. The use of the same sample batch with similar experimental conditions (Ne pressure medium, ruby scale, DAC, and cryostat) and small X-ray beam sizes permits reliable comparison on the magnetic and structural transitions.

ACKNOWLEDGMENTS. We thank C. Kenney-Benson, J. Liu, and C. Lu for their assistance; Z. Mao for helping with data analyses; and A. Wheat for editing the manuscript. We are also grateful to Wenge Yang, Yusheng Zhao, and Guoyin Shen for discussions. Portions of this work were performed at the High Pressure Collaborative Access Team (HPCAT Sector 16), Advanced Photon Source, Argonne National Laboratory. HPCAT operations are supported by the National Nuclear Security Administration, Department of Energy under Award DE-NA0001974 and by the Basic Energy Sciences, Department of Energy (DOE-BES) under Award DE-FG02-99ER45775, with partial instrumentation funding by the National Science Foundation. Advanced Photon Source, Argonne National Laboratory is supported by DOE-BES under Contract DE-AC02-06CH11357. Work at The University of Texas at Austin is supported by Energy Frontier Research in Extreme Environments (EFEE) and the Carnegie/DOE Alliance Center. Work at the Chinese Academy of Sciences is supported by National Science Foundation and Ministry of Science and Technology of China through research projects.

- McMillan PF (2002) New materials from high-pressure experiments. *Nat Mater* 1(1):19–25.
- Schilling JS (2006) Superconductivity in the alkali metals. *High Press Res* 26(1):145–163.
- Mao HK, et al. (1998) Elasticity and rheology of iron above 220 GPa and the nature of the Earth's inner core. *Nature* 396(6713):741–743.
- Oganov AR, Ono S (2004) Theoretical and experimental evidence for a post-perovskite phase of MgSiO_3 in Earth's D" layer. *Nature* 430(6998):445–448.
- Gao L, et al. (1994) Superconductivity up to 164 K in $\text{HgBa}_2\text{Ca}_{m-1}\text{Cu}_m\text{O}_{2m+2+5}$ ($m = 1, 2$, and 3) under quasihydrostatic pressures. *Phys Rev B* 50(6):4260–4263.
- Kamihara Y, Watanabe T, Hirano M, Hosono H (2008) Iron-based layered superconductor $\text{LaO}_{1-x}\text{Fe}_x\text{FeAs}$ ($x = 0.05\text{--}0.12$) with $T_c = 26\text{ K}$. *J Am Chem Soc* 130(11):3296–3297.
- Rotter M, Tegel M, Johrendt D (2008) Superconductivity at 38 K in the iron arsenide $\text{Ba}_{1-x}\text{K}_x\text{Fe}_2\text{As}_2$. *Phys Rev Lett* 101(10):107006.
- Wang XC, et al. (2008) The superconductivity at 18 K in LiFeAs system. *Solid State Commun* 148(11–12):538.
- Hsu FC, et al. (2008) Superconductivity in the PbO-type structure $\alpha\text{-FeSe}$. *Proc Natl Acad Sci USA* 105(38):14262–14264.
- de la Cruz C, et al. (2008) Magnetic order close to superconductivity in the iron-based layered $\text{LaO}_{1-x}\text{F}_x\text{FeAs}$ systems. *Nature* 453(7197):899–902.
- Huang Q, et al. (2008) Neutron-diffraction measurements of magnetic order and a structural transition in the parent BaFe_2As_2 compound of FeAs-based high-temperature superconductors. *Phys Rev Lett* 101(25):257003.
- Torikachvili MS, Bud'ko SL, Ni N, Canfield PC, Hannahs ST (2009) Effect of pressure on transport and magnetotransport properties in CaFe_2As_2 single crystals. *Phys Rev B* 80(1):014521.
- Alireza PL, et al. (2009) Superconductivity up to 29 K in SrFe_2As_2 and BaFe_2As_2 at high pressures. *J Phys Condens Matter* 21(1):012208.
- Mani A, Ghosh N, Paulraj S, Bharathi A, Sundar CS (2009) Pressure-induced superconductivity in BaFe_2As_2 single crystal. *EPL* 87(1):17004.
- Zhao K, et al. (2010) Superconductivity above 33 K in $\text{Ca}_{1-x}\text{Na}_x\text{Fe}_2\text{As}_2$. *J Phys Condens Matter* 22(22):222203.
- Pratt DK, et al. (2009) Coexistence of competing antiferromagnetic and superconducting phases in the underdoped $\text{Ba}(\text{Fe}_{0.953}\text{Co}_{0.047})_2\text{As}_2$ compound using X-ray and neutron scattering techniques. *Phys Rev Lett* 103(8):087001.
- Urbano RR, et al. (2010) Distinct high- T transitions in underdoped $\text{Ba}_{1-x}\text{K}_x\text{Fe}_2\text{As}_2$. *Phys Rev Lett* 105(10):107001.
- Yildirim T (2009) Strong coupling of the Fe-spin state and the As-As hybridization in iron-pnictide superconductors from first-principle calculations. *Phys Rev Lett* 102(3):037003.
- Fernandes RM, et al. (2010) Effects of nematic fluctuations on the elastic properties of iron arsenide superconductors. *Phys Rev Lett* 105(15):157003.
- Chu JH, et al. (2010) In-plane resistivity anisotropy in an underdoped iron arsenide superconductor. *Science* 329(5993):824–826.
- Kotegawa H, Sugawara H, Tou H (2009) Abrupt emergence of pressure-induced superconductivity of 34 K in SrFe_2As_2 : A resistivity study under pressure. *J Phys Soc Jpn* 78(1):013709.
- Colombier E, Bud'ko SL, Ni N, Canfield PC (2009) Complete pressure-dependent phase diagrams for SrFe_2As_2 and BaFe_2As_2 . *Phys Rev B* 79(22):224518.
- Kimber SAJ, et al. (2009) Similarities between structural distortions under pressure and chemical doping in superconducting BaFe_2As_2 . *Nat Mater* 8(6):471–475.
- Zhang SJ, et al. (2009) Effect of pressure on the iron arsenide superconductor Li_xFeAs ($x = 0.8, 1.0, 1.1$). *Phys Rev B* 80(1):014506.
- Zhang SJ, et al. (2009) Superconductivity at 31 K in the "111"-type iron arsenide superconductor $\text{Na}_{1-x}\text{FeAs}$ induced by pressure. *EPL* 88(4):47008.
- Liu QQ, et al. (2011) Pressure-induced isostructural phase transition and correlation of FeAs coordination with the superconducting properties of 111-type $\text{Na}_{1-x}\text{FeAs}$. *J Am Chem Soc* 133(20):7892–7896.
- Duncan WJ, et al. (2010) High pressure study of BaFe_2As_2 —the role of hydrostaticity and uniaxial stress. *J Phys Condens Matter* 22(5):052201.
- Yamazaki T, et al. (2010) Appearance of pressure-induced superconductivity in BaFe_2As_2 under hydrostatic conditions and its extremely sensitivity to uniaxial stress. *Phys Rev B* 81(22):224511.
- Smirnov GV (1999) General properties of nuclear resonant scattering. *Hyperfine Interact* 123/124(22):31–71.
- Rotter M, et al. (2008) Spin-density-wave anomaly at 140 K in the ternary iron arsenide BaFe_2As_2 . *Phys Rev B* 78(2):020503.
- Nomura T, et al. (2008) Crystallographic phase transition and high- T_C superconductivity in LaFeAsO : F. *Supercond Sci Technol* 21(12):125028.
- Qiu Y, et al. (2008) Crystal structure and antiferromagnetic order in $\text{NdFeAsO}_{1-x}\text{F}_x$ ($x=0.0$ and 0.2) superconducting compounds from neutron diffraction measurements. *Phys Rev Lett* 101(25):257002.
- Chandra P, Coleman P, Larkin AI (1990) Ising transition in frustrated Heisenberg models. *Phys Rev Lett* 64(1):88–91.
- Nandi S, et al. (2010) Anomalous suppression of the orthorhombic lattice distortion in superconducting $\text{Ba}(\text{Fe}_{1-x}\text{Co}_x)_2\text{As}_2$ single crystals. *Phys Rev Lett* 104(5):057006.
- Kasahara S, et al. (2012) Electronic nematicity above the structural and superconducting transition in $\text{BaFe}_2(\text{As}_{1-x}\text{P}_x)_2$. *Nature* 486(7403):382–385.
- Yildirim T (2008) Origin of the 150-K anomaly in LaFeAsO : competing antiferromagnetic interactions, frustration, and a structural phase transition. *Phys Rev Lett* 101(5):057010.
- Mazin II, Johannes MD (2009) A key role for unusual spin dynamics in ferropnictides. *Nat Phys* 5(2):141–145.
- Sturhahn W (2000) CONUSS and PHOENIX: Evaluation of nuclear resonant scattering data. *Hyperfine Interact* 125(1–4):149–172.